

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/322192890>

Synthesis and Characterization of Niobium and Tantalum Complexes with Bidentate Ligand and its use in Ring Opening Polymerization of ϵ -Caprolactone

Article in *Asian Journal of Chemistry* · January 2018

DOI: 10.14233/ajchem.2018.21144

CITATION

1

READS

106

5 authors, including:



Yahya Al-Khafaji

University of Babylon

28 PUBLICATIONS 195 CITATIONS

SEE PROFILE



Mohammed R. Al-Lami

Ministry of Higher Education and Scientific Research, Iraq, Baghdad

2 PUBLICATIONS 2 CITATIONS

SEE PROFILE



AHMED S. ABBAS

University of Babylon

21 PUBLICATIONS 31 CITATIONS

SEE PROFILE



Ameer A. Alameri

University of Babylon

28 PUBLICATIONS 4 CITATIONS

SEE PROFILE



Some of the authors of this publication are also working on these related projects:



E-LEARNING DEVELOPMENT [View project](#)



Three and Four Membered Heterocyclic Rings Substituted Derivatives of Phenobarbital and Using CPE for Determination of PB (II) [View project](#)



Synthesis and Characterization of Niobium and Tantalum Complexes with Bidentate Ligand and its use in Ring Opening Polymerization of ϵ -Caprolactone

YAHYA F. AL-KHAFAJI^{1,*}, MOHAMMED R. AL-LAMI², AHMED S. ABBAS¹, AMEER AL-AMERI¹ and AHMED FALAH ALBO MOUSA¹

¹Department of Chemistry, Faculty of Science, University of Babylon, Babylon, Iraq

²The Ministry of Higher Education and Scientific Research, Research Development Department, Baghdad, Iraq

*Corresponding author: Tel: +964 7805141952; E-mail: yfalkhafaji@gmail.com

Received: 21 October 2017;

Accepted: 30 November 2017;

Published online: 31 December 2017;

AJC-18722

Reaction of two equivalents of the bidentate 2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂OH]₂ with one equivalent of niobium pentachloride gave the complex Nb{2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂O]₂}₂ (**1**). Similar use of two equivalents of the same ligand with one equivalent tantalum pentachloride afforded Ta{2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂O]₂}₂ (**2**). The molecular structure of complexes **1** and **2** have been characterized by IR and ¹H NMR. Both complexes were investigated as catalysts for polymerization of cyclic esters (ϵ -caprolactone) with no solvent at various time at 110 °C. In all cases the polymer produced was of high yield percent.

Keywords: Niobium(V), Tantalum(V), Phenolate, ϵ -Caprolactone, Ring opening polymerization.

INTRODUCTION

Biodegradable polymeric material produced *via* ring opening polymerization (ROP) of ϵ -caprolactone continues to catch much attention by reason of a wide range of applications [1,2]. A variety of catalysts have been used as initiators for ring opening polymerization and coordination chemistry shows a significant role in this process, the use of niobium and tantalum compounds received more attention due to no toxicity related with these metals. According to the literature a few papers published on these metals complexes as catalysts toward polymerization of lactide, lactone or ethylene [3-6]. The use of Schiff base ligation has received more interest because of easy to prepare [7] and versatile applications of Schiff base and their complexes as biological activity, antifungal properties, anticancer properties, application in modern technologies, application in synthesis and chemical analysis [8-13].

In this paper, two complexes of niobium and tantalum were synthesized, characterized and their catalytic behaviour was investigated. As compared with one equivalent of 2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂OH]₂ prepared by Redshaw *et al.* [14] and Müller *et al.* [15], we have found that by employing two equivalent of 2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂OH]₂ ligand can be beneficial in term of control of polymerization.

EXPERIMENTAL

Dried environment was carried out throughout the experiment. Solvents were dried before use. Infrared spectra were recorded

using Nicolet Avatar 360 FTIR spectrometer. ¹H NMR were recorded at 400 MHz in a (VXR 400 S) spectrometer.


Synthesis of Nb{2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂O]₂}₂ complex (1**):** A toluene solution of 20 mL of 2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂OH]₂ (1 g, 1.99 mmol) and NbCl₅ (1.12 g, 0.99 mmol) was dissolved in 10 mL toluene and mixed with ligand solution. The mixture was refluxed for 6 h followed by the removal of volatiles and extracted the solid into acetonitrile (20 mL) to give red coloured solid complex **1**.

Synthesis of Ta{2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂O]₂}₂ complex (2**):** By following same procedure as described for synthesis of complex **1**, the complex **2** was synthesized by the reaction of TaCl₅ (1.21 g, 0.99 mmol) with 20 mL of 2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂OH]₂ (1.00 g, 1.99 mmol) to give pink coloured solid complex **2**.

Ring opening polymerization: Complex **1** or **2** (0.30 g, 266.46 μ mol), ϵ -caprolactone (6.08 mL, 52.39 mmol) and alcohol (0.01 mL, 118.3 μ mol) mixed together in absence of solvent and the system was placed in an oil bath at 100 °C. After 1 h, the mixture quenched by added methanol (250 mL).

RESULTS AND DISCUSSION

The compound 2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂OH]₂ was prepared according to reported procedure [4,14]. Reaction of ligand with toluene solution of niobium pentachloride (2:1) ratio and tantalum pentachloride (2:1) ratio has resulted in the formation of Nb{2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂O]₂}₂ (**1**) complex and Ta{2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂O]₂}₂ (**2**) complexes.

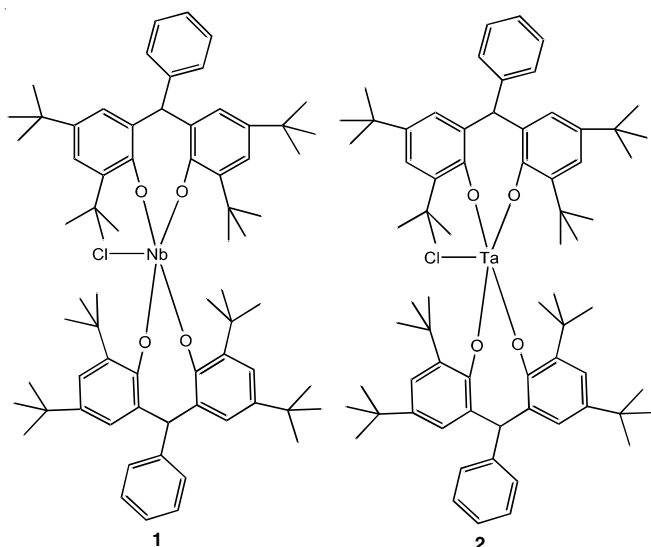

Structure of Nb{2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂O]₂}₂ (**1**) and Ta{2,2'-PhCH[4,6-(*t*-Bu)₂C₆H₂O]₂}₂ (**2**)

Infrared spectra: The IR spectra of both complexes presented a characteristic absorption single at 2900 cm⁻¹ belonging to *t*-butyl group while peaks at 3200-3100 cm⁻¹ shifted to shorter wave length indicated that coordination has happened through -OH group.

¹H NMR spectra: The ¹H NMR spectra of complexes was performed in CDCl₃ at room temperature. The spectrum of complex **1** revealed the signals at 1.27 (s, 36H, *t*-Bu), 1.30 (s, 36H, *t*-Bu), 3.77 (s, 1H, CH-bridge) and 6.67-7.51 (m, 18H, Ar-H) (Fig. 1). For complex **2**, ¹H NMR spectrum showed the signals at 1.29 (s, 18H, *t*-Bu), 1.42 (s, 18H, *t*-Bu), 4.43 (s, 1H, CH bridge) and 7.15-7.43 (m, 18H, Ar-H) (Fig. 2).

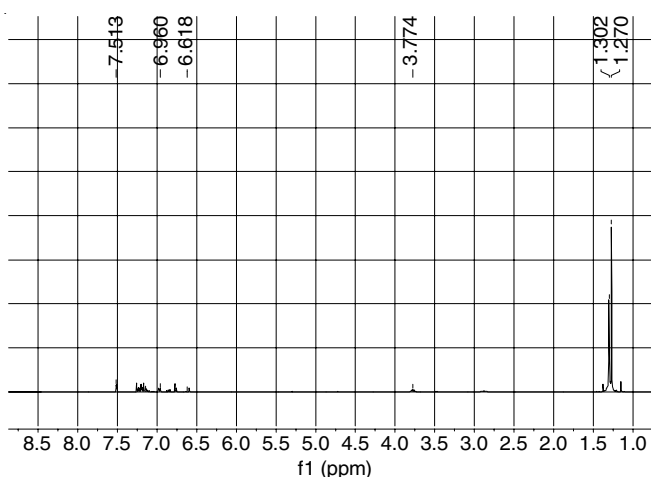


Fig. 1. ¹H NMR spectrum of complex **1**

Ring opening polymerization of ϵ -caprolactone: The ability of synthesized complexes toward the ring opening polymerization of ϵ -caprolactone were assessed (**Scheme-I**). Polymerization of ϵ -caprolactone by complexes **1** and **2** which includes the phenoxide group were noted to be active (Table-1). The polymer molecular weight (M_n) obtained by Ta catalyst is much lower as compared to Nb catalyst [16].


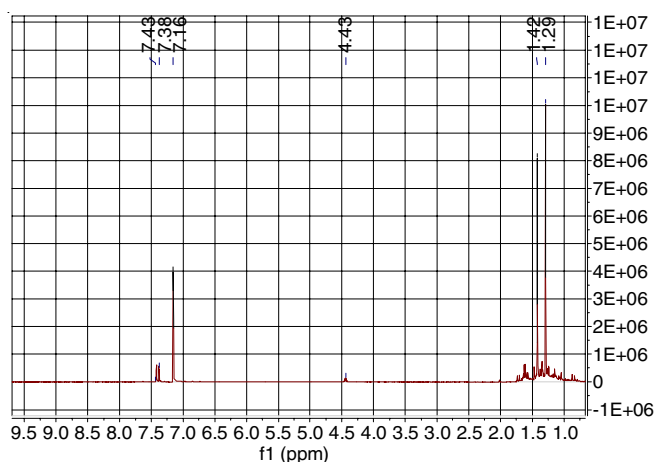


Fig. 2. ¹H NMR spectrum of complex **2**

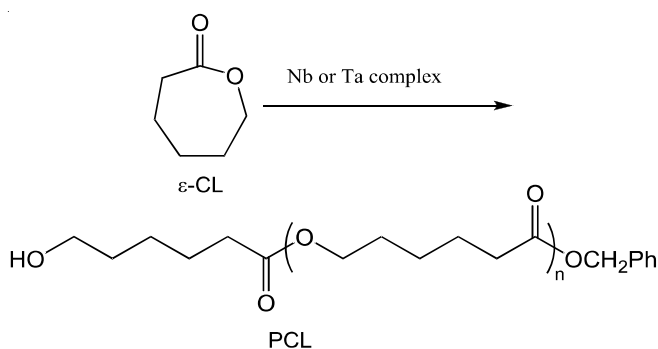

Scheme-I: Ring opening polymerization of ϵ -CL

TABLE-1
POLYMERIZATION OF ϵ -CAPROLACTONE
USING COMPOUNDS **1** AND **2**^a

Catalyst	Yield (%)	Time (min)	M_n^b	PDI ^c
Nb complex	81	30	12900	1.10
Ta complex	77	40	6500	1.29

^aConditions: 0.0123 mol of complexes; 1.0 M ϵ -CL in toluene. CL: [cat] : BnOH = 200:1:1. ^bfrom GPC.

ACKNOWLEDGEMENTS

The authors thanks Ministry of Higher Education and Scientific Research, Research and Development Department and Department of Chemistry, Faculty of Science, University of Babylon, Babylon, Iraq for supporting this work.

REFERENCES

- A.L. Sisson, D. Ekinici and A. Lendlein, *Polymer*, **54**, 4333 (2013); <https://doi.org/10.1016/j.polymer.2013.04.045>.
- M.A. Woodruff and D.W. Huttmacher, *Prog. Polym. Sci.*, **35**, 1217 (2010); <https://doi.org/10.1016/j.progpolymsci.2010.04.002>.
- Y. Al-Khafaji, X. Sun, T.J. Prior, M.R. Elsegood and C. Redshaw, *Dalton Trans.*, **44**, 12349 (2015); <https://doi.org/10.1039/C5DT00272A>.
- T.K. Saha, M. Mandal, M. Thunga, D. Chakraborty and V. Ramkumar, *Dalton Trans.*, **42**, 10304 (2013); <https://doi.org/10.1039/c3dt50752a>.
- C. Chi-T, L.H. Doerrer, V.C. Williams and M.L.H. Green, *J. Chem. Soc., Dalton Trans.*, 967 (2000).
- J.M. Decams, S. Daniele, L.G. Hubert-Pfalzgraf, J. Vaissermann and S. Lecocq, *Polyhedron*, **20**, 2405 (2001); [https://doi.org/10.1016/S0277-5387\(01\)00834-8](https://doi.org/10.1016/S0277-5387(01)00834-8).

7. W. Qin, S. Long, M. Panunzio and S. Biondi, *Molecules*, **18**, 12264 (2013); <https://doi.org/10.3390/molecules181012264>.
8. S. Sundriyal, R.K. Sharma and R. Jain, *Curr. Med. Chem.*, **13**, 1321 (2006); <https://doi.org/10.2174/092986706776873023>.
9. M. Jesmin, M.M. Ali and J.A. Khanam, *Thail. J. Pharm. Sci.*, **34**, 20 (2010).
10. K. Tanaka, R. Shimoura and M.R. Caira, *Tetrahedron Lett.*, **51**, 449 (2010); <https://doi.org/10.1016/j.tetlet.2009.11.062>.
11. P. Mastalerz, Organic Chemistry Edition, Wroclaw, Poland (1996).
12. X. Wang, K.-Q. Zhao, Y. Al-Khafaji, S. Mo, T.J. Prior, M.R.J. Elsegood and C. Redshaw, *Eur. J. Inorg. Chem.*, 1951 (2017); <https://doi.org/10.1002/ejic.201601415>.
13. R. Hassan, H. Arida, M. Montasser and N.A. Latif, *J. Chem.*, **Article ID 240568** (2013); <https://doi.org/10.1155/2013/240568>.
14. Y. Al-Khafaji, T.J. Prior, M.R.J. Elsegood and C. Redshaw, *Catalysts*, **5**, 1928 (2015); <https://doi.org/10.3390/catal5041928>.
15. E. Müller, A. Schick and R. Mayer, *Eur. J. Inorg. Chem.*, **93**, 2649 (1960); <https://doi.org/10.1002/cber.19600931133>.
16. T. Saha, M. Mandal, M. Thunga, D. Chakraborty and V. Ramkuma, *Dalton Trans.*, **42**, 10304 (2013); <https://doi.org/10.1039/C3DT50752A>.