

Spectroscopic study of UV-VIS electronic transitions of Ni²⁺ ions in different phases of Sol- Gel process

دراسة طيفية للانتقالات الالكترونية (UV-VIS) لأيون النيكل Ni²⁺ لمختلف أطوار عملية صول جل (Sol-Gel)

Qussay Mohammed Salman

Laser Physics Department, College of science for women, University of Babylon ,
Babylon, (IRAQ) E-mail:qusay_63@yahoo.com

ABSTRACT

Allowed and forbidden Electronic transition of Ni²⁺ ions have been investigated in solution, sol and Xerogel .Two complexes NiCl₂.6H₂O and Ni(NO₃)₂.6H₂O have been dissolved in (water and ethanol) and doped in silica matrices using sol-gel technique. The molar ratio of TEOS: H₂O: Ethanol which adopted in this study were 1:8:12 of PH value = 1 at 60°C. It is found that up to 150°C the Xerogel samples as well as in sol and solution Ni²⁺ ions have octahedral symmetry. The Racah parameter (B) and ligand field strength (Δ) has been calculated for Ni²⁺ ions in solution it is found Δ /B=0.85, while in silica matrices ligand field strength has been increased to be greater than 0.9 .It also found that absorbance peaks also have red shift with increasing draying time .

Key words : Ni²⁺ ions, Sol-Gel glasses , spectroscopy

الخلاصة

الانتقالات الالكترونية المسموحة والممنوعة طيفيا لأيون Ni²⁺ تمت متابعتها خلال مراحل عملية الصول جل حيث تم اذابة المركبين NiCl₂.6H₂O و Ni(NO₃)₂.6H₂O في كلا من الماء والكحول ومن ثم إجراء تطعيم في مصفوفات سليكا باستخدام تقنية sol-gel . ان النسبة المولارية لكل من TEOS: H₂O: Ethanol المعتمدة في هذا البحث هي 1:8:12 وقيمة PH هي 1 عند درجة حرارة 60°C . وقد وجد ان ايون Ni²⁺ في نماذج Xerogel المحضرة وحتى درجة 150°C وكذلك في طور sol وكذلك المحاليل يمتلك تناظر ثنائي . وقد تم حساب معامل Racah (B) وكذلك شدة المجال اليكاند(Δ) لأيون Ni²⁺ في المحاليل حيث وجدت Δ /B=0.85 بينما في مصفوفات سليكا كانت قيمته اكثر من 0.9 . وجد في هذا البحث كذلك ان قيم الامتصاصية يكون لها انحراف باتجاه الاطوال الموجية الطويلة بزيادة زمن التجفيف للنماذج. الكلمات المفتاحية : ايون Ni²⁺ , صول جل زجاج , أطياف

I. INTRODUCTION.

Sol-gel technique is widely have been used to prepare different of mixed-metal oxides, nanomaterials and organic-inorganic hybrids materials by incorporating different cations or molecules in a silica host [1–5]. An important characteristic of the sol-gel process is the possibility of controlling all stages, which occur during the passage through molecular precursor to the final product. Over the last few decades Sol-gel methods prepared successfully different garnets, aluminates, cobaltates and superconductors [6 – 8].

Nickel oxide films were have been deposited from mixtures of nickel nitrate, [Ni(NO₃)₂.6(H₂O)], in alcohol or ethylene glycol C₂H₆O₂ [9,10] solutions but the stability of nickel nitrate during heat processing limited its use to finite applications. The use of nickel sulphate heptahydrate NiSO₄.7H₂O with addition of several other compounds has been also studied. More studies confirm that the heat treatment is very effective parameter [11–14]. The same effect has been found for coating with sols of nickel chloride (NiCl₂.6H₂O) in ethylene glycol and butanol for the deposition process of NiOxHy thin films [15, 16]. The addition of tetraethoxysilane (TEOS) to the alcoholic mixture of anhydrous halide showed to be a suitable procedure, to prepare electrochromic Ni-based thin films, the results have also shown that coatings have been more

hardness, better adhesion and maintaining rather high[17]. another Mixture of nickel nitrate with ethylene glycol and tetraethoxysilane was also suggested [10].

The requirement to enhance solid-state lasers, optoelectronic communication devices, and optical quality of the materials has increase the interest in activator doped glass. Glass ceramic (GC) materials are one of the most important hybrid optical materials required which can be produced by controlling the nucleation and crystallization of glass. This type of nanocomposite materials can be used as hosts for activators ions so they can combine the advantages of both glass for it is easy made and doped crystal as optical activity [18].

In this paper the electronic transitions for both allowed and forbidden of Ni²⁺ ion (d⁸) have been investigated. According to the Tanabe-Sugano diagram Figure 1 for Ni²⁺, the strength of the crystal field, Δ(10Dq), is determined by the energy difference between the ³A_{2g} and ³T_{2g} states, also other states clearly in the diagram which is very well known by spectroscopists[19]. The samples which prepared by sol gel technique have been studied in different phases :solutions , sol, Xerogel and glasses by using UV-VIS absorption spectra, Finally verifying the Ni²⁺ ions cooperated in silica network at different annealing temperature.

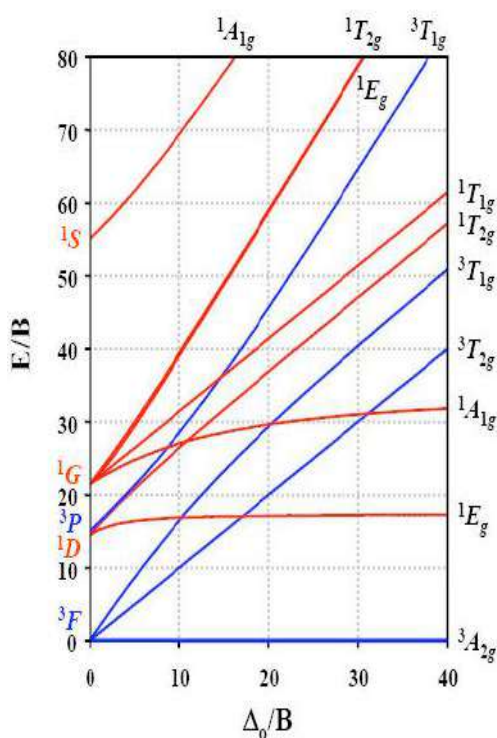


Figure (1) Energy level diagram for a d⁸ ion in octahedral ligand fields . [19]

II. EXPERIMENTAL METHOD.

In order to have spectroscopy study the samples should be basically transparent clearly and free crack, so many samples have prepared with different sol gel parameters { pH ,R- molar ratio, ageing temperature T } at different concentrations of Ni ions.

Different R-molar ratio, of water/alkoxide, (2, 5, 8, 10, 25 and 60) were used at specific pH, ageing temperature (T) and Ni ion concentration. To get more exact value of R, the chromium salts were dissolved in ethanol instead of water. The final pH value has been modify to one (pH=1) in order to get a maximum transparency [20], since the other samples became quasi opaque and the samples transfer totally opaque for value of pH greater than four.

The schematic diagram for preparing samples is shown in Fig.2.

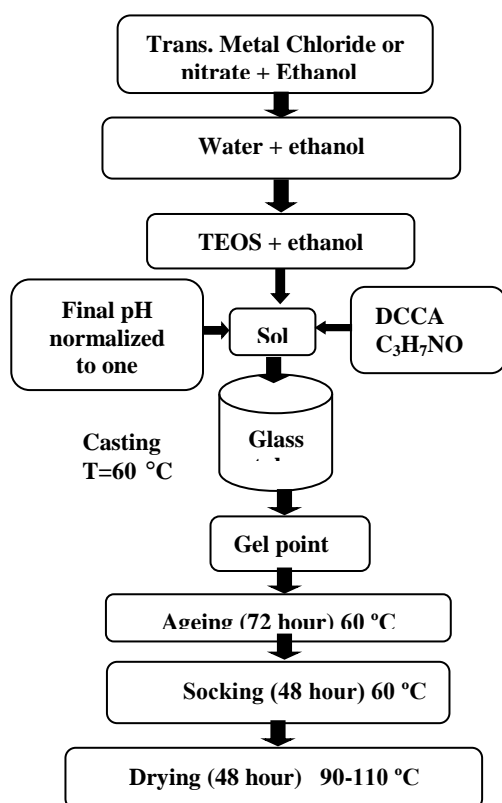


Figure (2) Schematic diagram of preparing Xerogel samples

The ageing temperature has been chosen to be 60°C to get optimum polymerization at minimum gelling time. So the optimum value for R, pH and T which were employed in this work are 8, 1 and 60°C respectively. N, N dimethyl formamide (C₃H₇NO) was used in this work as drying control chemical additive (DCCA). In our study, saturation occurs at Ni ion concentration about 10⁻¹ M, while at concentrations lower than 10⁻³ M the forbidden transitions have never been observed. Hence the Ni²⁺ concentrations adopted in this work were (10⁻¹-10⁻³) M. All the employed concentrations were increasing ten times after drying to 200 °C due to the contraction phenomena. Room temperature absorption spectra were measured using double beam UV-VIS -2700 Spectrophotometer supplied by CECIL company.

III. RESULTS AND DISCUSSION.

Two complexes (NiCl₂.6H₂O) & (Ni (NO₃)₂.6H₂O) are dissolved in water & ethanol. Fig. (3) shows absorbance spectra of NiCl₂.6H₂O dissolved in H₂O for different concentrations .

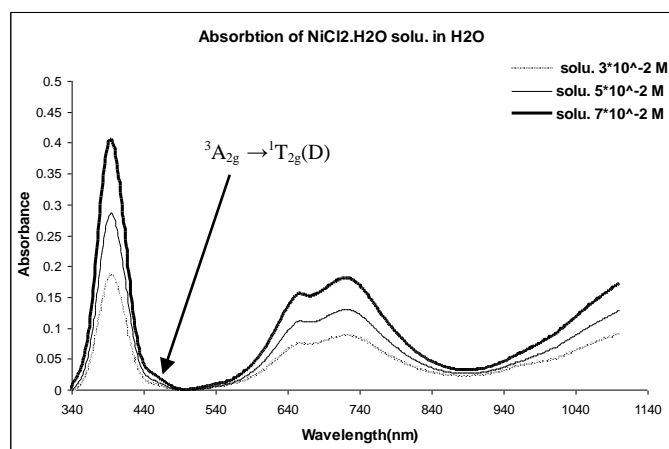


Figure (3)

The transition ν_2 (${}^3A_{2g} \rightarrow {}^3T_{1g}$) is observed at 726nm(13774.104cm^{-1}) and the transition ν_3 (${}^3A_{2g} \rightarrow {}^3T_{1g}$ (p)) which has more intensity than (ν_2) at 398nm (25125.628cm^{-1}). So ratio of two allowed transition $\nu_3/\nu_2 \approx 1.824$ by using Level method [19] obtain $Dq/B=0.9$, so the first transition ν_1 (${}^3A_{2g} \rightarrow {}^3T_{2g}$) and B can be calculated to be at 8347.941cm^{-1} , 927.544cm^{-1} respectively.

When dissolved NiCl₂.6H₂O complex in Ethanol as in H₂O there's also Three transitions observed ν_2 at 760nm (13157.89cm^{-1}) and transition ν_3 at 410nm(24390.24cm^{-1}) Also spin-forbidden transition has observed at 700(nm) which attributed to ${}^3A_2 \rightarrow {}^1E(D)$, while the transition ${}^3A_2 \rightarrow {}^1E(D)$ is not observed in ethanol solution . There is also another absorption peak in concentration 10^{-1}M at 283nm which may be referred to the charge transfer (C.T) fig.(4) spectra this transition not clear in other concentration.

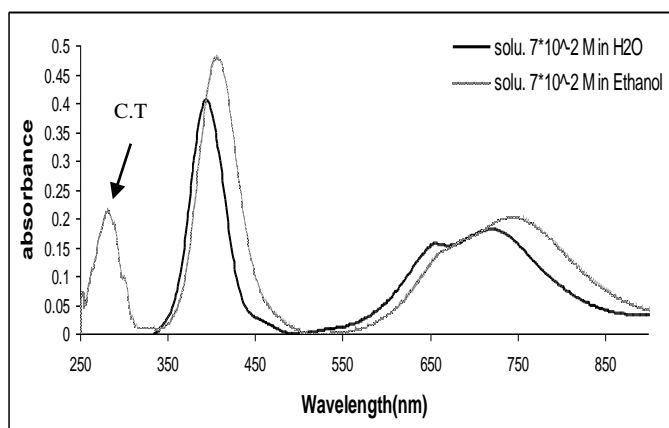


Figure (4) The absorption spectra of NiCl₂.6H₂O in Water and Ethanol

as in H₂O, B and Δ can be calculated by using Level method $Dq/B=0.85$ obtain $\nu_1=7739.93\text{cm}^{-1}$ and $B=910.58\text{cm}^{-1}$, comparison between The two solvent it is easily noticed the absorbance in Ethanol is more than in H₂O ,the absorption Peak in Ethanol have red shifted fig.(4) which indicating a decrease in ligand field strength.

The absorption spectra of Ni^{2+} in the complex $(Ni(NO_3)_2 \cdot 6H_2O)$ dissolved in water at several concentrations are shown in Figure (3-6).

The transition (ν_2) is observed at 724nm($13812.154cm^{-1}$) and the transition (ν_3) which has more intensity than (ν_2) observed at 394nm($25380.710cm^{-1}$).

spin-forbidden transition has observed also in this solution at 655nm which attributed to $^3A_2 \rightarrow ^1E(D)$ Fig. (5), another spin-forbidden transition has observed at 355nm which attributed to $^3A_2 \rightarrow ^1A_{1g}$ which belong to (1G) state Fig. (5).

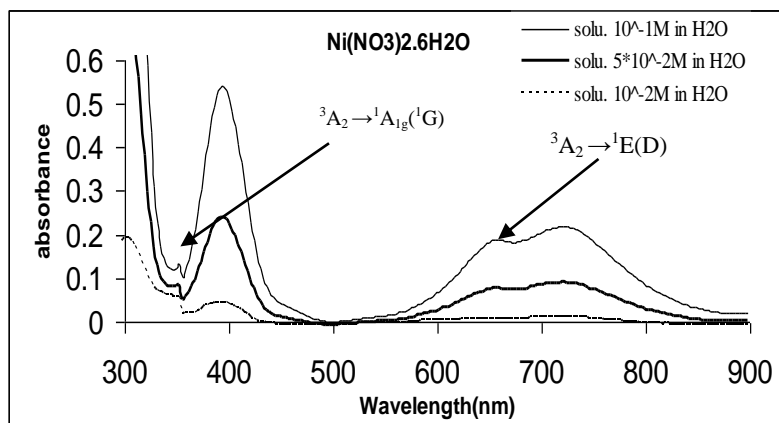


Figure (5) The absorption spectra of $Ni(NO_3)_2 \cdot 6H_2O$ in water

Fig.(6) illustrates the absorption spectra of Ni^{2+} in the two complex $(Ni(NO_3)_2 \cdot 6H_2O)$ and $NiCl_2 \cdot 6H_2O$ which are dissolved in water comparison between The two solvent it is easily noticed the absorbance of Ni^{2+} in $NiCl_2 \cdot 6H_2O$ is more than in $Ni(NO_3)_2 \cdot 6H_2O$, it is also noticed the absorption Peaks in $NiCl_2 \cdot 6H_2O$ have red shifted which indicating a decrease in ligand field strength . Nickel (II) complexes appears in this work to be $(Cl^- < NO_3^-)$.

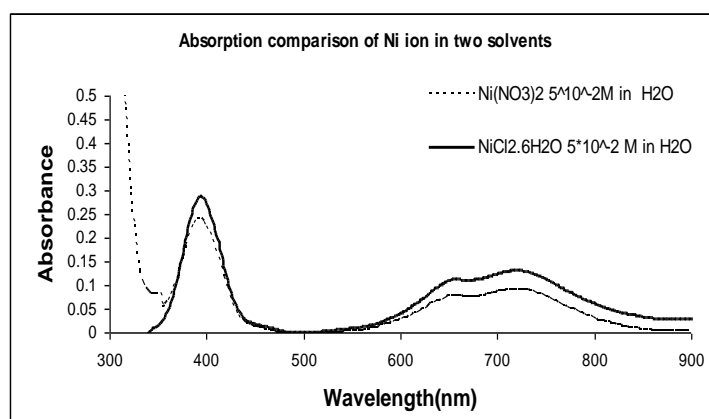


Figure (6) The absorption spectra of $Ni(NO_3)_2 \cdot 6H_2O$ and $NiCl_2 \cdot 6H_2O$ in water

Fig.(7) shows the absorption spectra of $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$ SOL for different concentrations as in the solution there are mainly three transitions observed their intensity were lower than that in solution and this may be attributed to decreasing of the concentration of Ni^{2+} after adding (H_2O , TEOS, DMF, Ethanol, and HNO_3) in sol gel process. The two absorption peaks were shifted toward short wavelength compared to that of ethanol solution, which may be explain by increasing in the $\Delta(10Dq)$ in sol compared to that in ethanol solution.

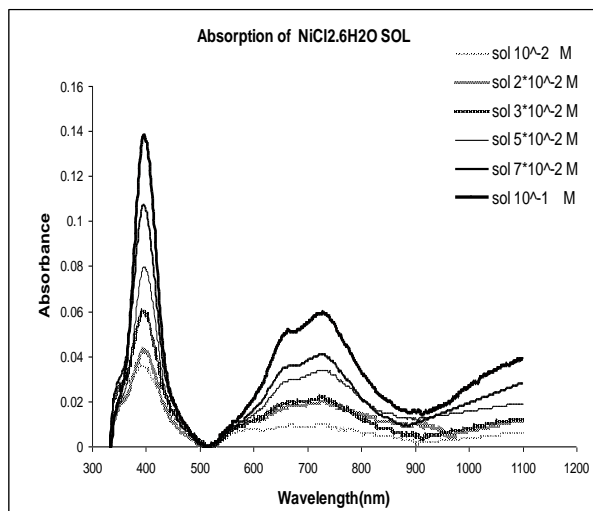


Figure (7). The absorption spectra of $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$ SOL

The transitions observed are ${}^3A_{2g} \rightarrow {}^3T_{1g} (v_2)$ at 735 nm and the third transition ${}^3A_{2g} \rightarrow {}^3T_{1g} (p) (v_3)$ at 400nm. Also there is a spin-forbidden transition ${}^3A_2 \rightarrow {}^1E(D)$ observed at 665nm so the transitions in Sol has blue shifted compare to the solution due to increasing in the $\Delta(10Dq)$.

Fig.(8) shows the absorption spectra of $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$ Xerogel for different concentrations after 6 days. The transition ${}^3A_{2g} \rightarrow {}^3T_{1g}(v_2)$ is observed at $\sim 735\text{nm}$ (13605.44cm^{-1}) and the transition ${}^3A_{2g} \rightarrow {}^3T_{1g}(p) (v_3)$ at $\sim 397\text{nm}$ (25188.91cm^{-1}) which have a little red shift with concentration increasing. Also there are forbidden transitions observed in the samples at (765, 630, 472)nm in addition to ${}^3A_2 \rightarrow {}^1E(D)$ at $\sim 670\text{nm}$.

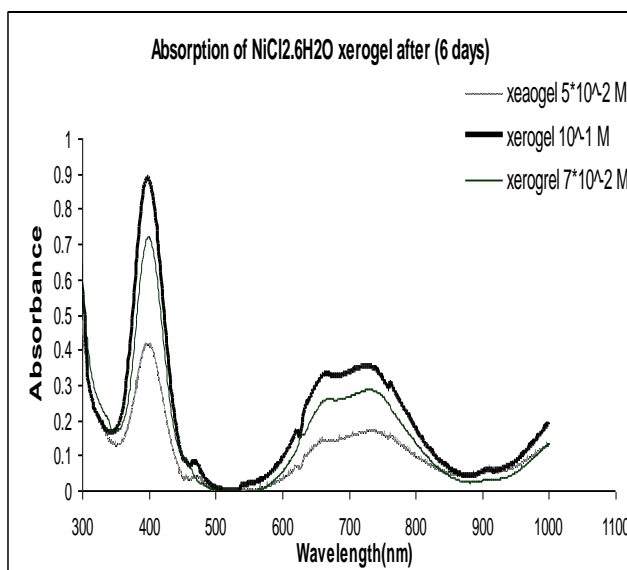


Figure 8. The absorption spectra of $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$ Xerogel for different concentrations after 6 days

It is very clear the absorption Peaks of Ni^{+2} ions in Xerogel have shifted towards short wavelength compare to that in solution Fig.(9) which may be explain by increasing in strength of ligand field strength in silica matrices, so it can be calculated Dq/B in Xerogel is greater than 0.9

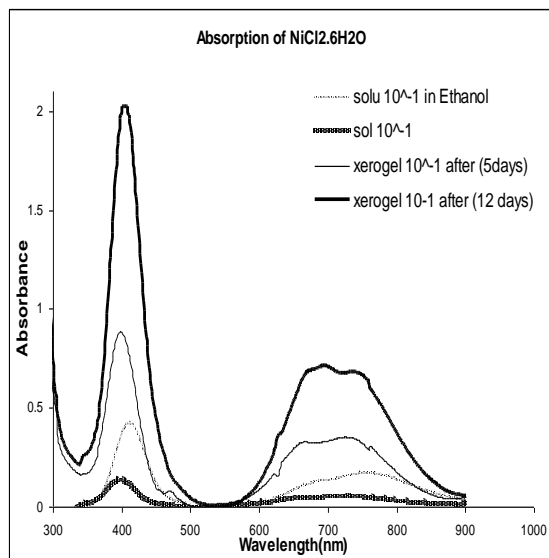


Figure 9. The absorption spectra of Ni^{+2} ions in solution , Sol and Xerogel of complex $NiCl_2.6H_2O$

Fig.(10) shows the absorption spectra of $NiCl_2.6H_2O$ Xerogel for after 6, 12 and 30 days., the samples have the same transitions with the red shift for all transitions,

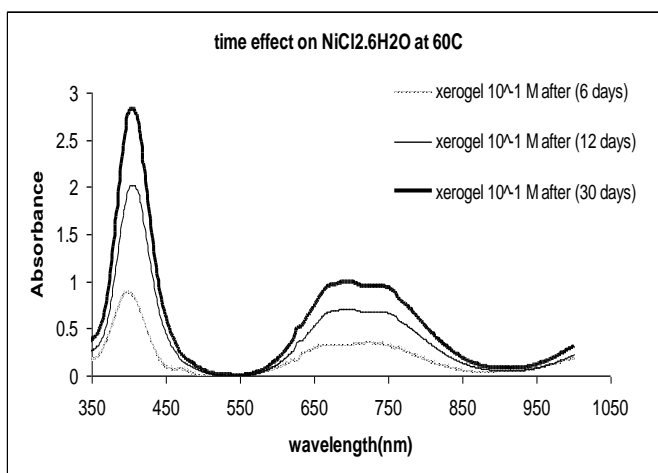


Figure 10. The absorption spectra of Ni^{+2} ions Xerogel after 6, 12 and 30 days of complex $NiCl_2.6H_2O$

also the increases in concentrations causes red shift Fig.(11) shows this shifted for peak around 400nm for different concentrations.

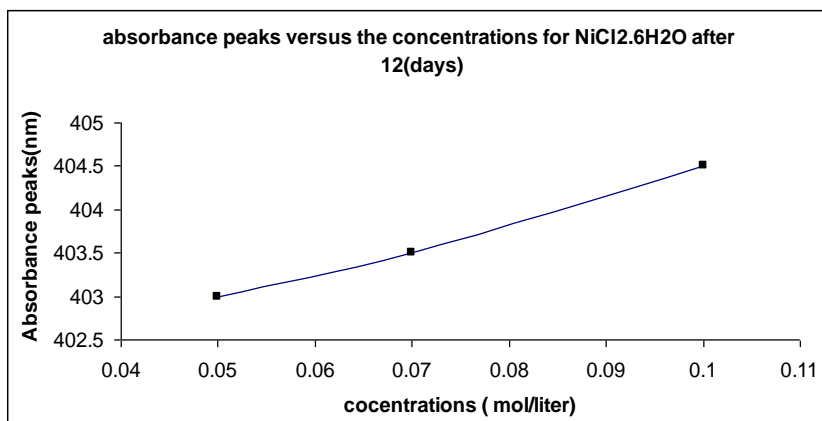


Figure 11. illustrated the shift of absorbance peaks versus the concentrations for NiCl₂.6H₂O after 12 days

Fig.(12) shows the absorption spectra of NiCl₂.6H₂O Xerogel for different temperatures, The absorbance increases as temperatures arise from 60°C to 150°C. The intensity of transition (v_3) is more than (v_2) for all temperatures ,also the separation between two transitions $^3A_{2g} \rightarrow ^3T_{1g}(v_2)$ at ~700nm and the forbidden transition $^3A_2 \rightarrow ^1E(D)$ at ~ 660nm become more obviously when temperature arise from 60 °C to 150°C . There is also a shoulder at 630nm may attribute to forbidden transitions.

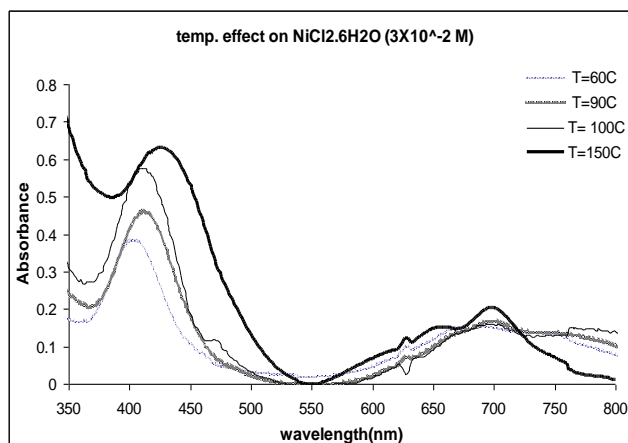


Figure 12. absorption spectra of Ni²⁺ ions in NiCl₂.6H₂O Xerogel for different temperatures

The absorbance peak of the transition (v_3) have red shift with temperatures increases as show in Fig.(13).

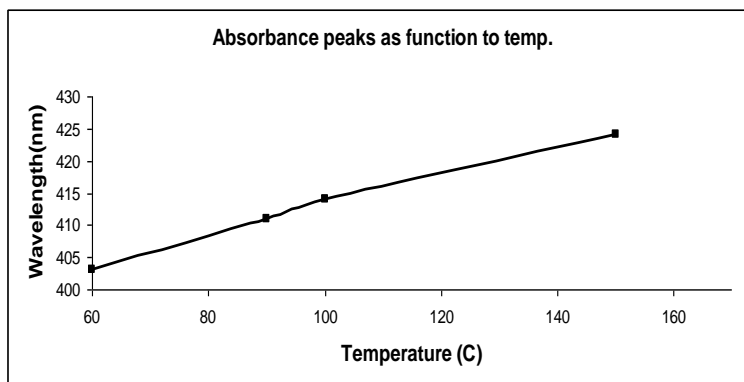


Figure 13. absorbance peak of Xerogel for transition (v_3) as function of temperature

IV. CONCLUSIONS

Our studies show that Ni^{2+} ion in the two complexes $NiCl_2 \cdot 6H_2O$ and $Ni(NO_3)_2 \cdot 6H_2O$ have octahedral symmetry in solution (Ethanol & water), sol and xerogel up to $150^\circ C$. the absorption Peaks of Ni^{2+} ions in silica matrices of Xerogel have shown blue shifted compare to that in solution and Sol, so the ligand field strength (Δ) increasing, also (Δ) has shown increasing in nitrate compare to chloride. Also the absorbance peaks after 12 and 30 days have red shift in Xerogel compare with same sample after 6 days. the absorbance spectra show the Ni^{2+} ion have cooperated in silica matrices in all drying conditions (temperature & drying time).

REFERENCES

- [1] C. J. Brinker, G. W. Scherer, "Sol-Gel Science: The Physics and Chemistry of Sol-Gel Processing". Academic Press, London, 1990.
- [2] D. Dutta "Optimization of process parameters and its effect on particle size and morphology of ZnO nanoparticle synthesized by sol-gel method", Journal of Sol-Gel Science and Technology, January, 77, pp 48-56, 2016
- [3] A. Katelnikovas, J. Barkauskas, F. Ivanauskas, A. Beganskiene, A. Kareiva, "Aqueous Sol-Gel Synthesis Route for the Preparation of YAG: Evaluation of Sol-Gel Process by Mathematical Regression Model" Journal of Sol-Gel Science and Technology, 41, pp. 193 – 201, 2007.
- [4] J.D. Mackenzie, E. P. Bescher, "Chemical Routes in the Synthesis of Nanomaterials Using the Sol-Gel Process" Accounts of Chemical Research, 40, pp. 810 – 818, 2007.
- [5] T. Sakai, T. Katashima, T. Matsushita and U. Chung, "Sol-gel transition behavior near critical concentration and connectivity" , Polymer Journal 48, pp 629–634, 2016
- [6] L. S. Cividanes, T. M. B. Campos, L. A. Rodrigues, D.D. Brunelli & Gilmar P., "Review of Mullite Synthesis Routes By Sol-Gel Method", Journal of Sol-Gel Science and Technology, 55, pp.111–125, 2010.
- [7] A. Katelnikovas, T. Justel, D. Uhlich, J.E. Jorgensen, S. Sakirzanovas, A. Kareiva, "Characterization of Cerium doped Yttrium Aluminium Garnet Nanopowders Synthesized via Sol-Gel Process", Chemical Engineering Communications, 195, pp. 758 – 769, 2008.
- [8] T. Klemkiene, R. Raudonis, A. Beganskiene, A. Zalga, I. Grigoraviciute, A. Kareiva, "Scandium and Gallium Substitution Effects in the $(Y_{1-x}Sc_x)Ba_2Cu_4O_8$ and $(Y_{1-x}Ga_x)Ba_2Cu_4O_8$ Superconducting Oxides Materials", Chemistry and Physics, 119, pp. 208 – 213, 2010.

- [9] F.H.Moser, N. R. Lynam., “Electrochromic coating and method for making same”, US Patent 4,959,247 1990.
- [10] T. Miki, K. Yoshimura, Y. Tai, M. Tazawa, P. Jin, S. Tanemura Electrochromic properties of nickel oxide thin films prepared by the Sol-Gel method”. Proc SPIE 2531, pp.135–142, 1995.
- [11] A. Šurca, B. Orel, ,“Sol-Gel derived hydrated nickel oxide electrochromic films: optical, spectroelectrochemical and structural properties”. J Sol-Gel Sci Technol, 8, pp.743–749,1997.
- [12] Mardanpour, M. Mahdi and Y. Soheila , "Characterization of a microfluidic microbial fuel cell as a power generator based on a nickel electrode" **Biosens Bioelectron**, 79, pp.327-33, 2016.
- [13] R.C. Koros^{ec}, P. Bukovec “The role of thermal analysis in optimization of the electrochromic effect of nickel oxide thin films, prepared by the Sol-Gel method”, part II. *Thermochimica Acta*, 410,PP. 65–71, 2004.
- [14] R.C. Koros^{ec}, P. Bukovec, “Sol-Gel prepared NiO films for electrochromic application”, *Acta Chim Slov* ,53,pp.137–147 2006.
- [15] P.K. Sharma,M.C.A. Fantini, A.Gorenstein,“Synthesis, characterization and electrochromic properties of NiOxHy thin film prepared by a Sol-Gel method”, *Solid State Ionics* 113–115,pp.457–463, 1998.
- [16] P.K. Sharma, M.C.A.Mracia, H.Fischer, A.F.Craievich, A. Gorenstein, “Factors influencing the electrochromic properties of nickel oxide thin films derived from Sol-Gel methode by dip-coating”, *Mat. Res. Soc. Symp. Proc*, 547,pp. 351–356, 1999.
- [17] F.H. Moser, N.R.Lyman, “Method for deposition of electrochromic layers”, United States Patent, Appl. No. 4855161,1989.
- [18] L. R. Pinckney and G. H. Beall, “Transition element-doped crystals in glass,” *Proc. SPIE* ,**4452**, pp.93-99 ,2001.
- [19] S.Sugano, Y.Tanabe and H. Kamimura, "Multiplets of Transition Metal Ions in Crystals", New York: Academic, USA, 1970.
- [20] R.K.Ller, "The Chemistry of Silica Solubility, Polymerization Colloid and Surface Properties and Biochemistry ", John Wiley and Sons, 1979.